

Phenomenological Transport Equation for the Cuprate Metals

P. Coleman¹, A. J. Schofield¹ and A. M. Tsvelik²

¹*Serin Laboratory, Rutgers University, P.O. Box 849, Piscataway, New Jersey 08855-0849*

²*Department of Physics, University of Oxford, 1 Keble Road, Oxford OX1 3NP, UK*

We observe that the appearance of two transport relaxation times in the various transport coefficients of cuprate metals may be understood in terms of scattering processes that discriminate between currents that are even, or odd under the charge conjugation operator. We develop a transport equation that illustrates these ideas and discuss its experimental and theoretical consequences.

72.15.Nj, 71.30+h, 71.45.-d

The normal state of the cuprate superconductors exhibits the extraordinary feature of two transport relaxation time-scales. In optimally doped compounds, conductivity and photo-emission measurements indicate a scattering rate which grows linearly with temperature $\tau_{tr}^{-1} = \eta T$, where for YBCO $\eta \approx 2$. [1] By contrast, Hall constant and magneto-resistance measurements indicate that the cyclotron relaxation rate τ_H^{-1} has a qualitatively different *quadratic* temperature dependence.

$$\tau_H^{-1} = \frac{T^2}{W_s} + b_i. \quad (1)$$

Experimentally, τ_H^{-1} is inferred from the Hall angle $\theta_H = \omega_c \tau_H$, manifested in both the Hall conductance $\sigma_{xy} = \sigma_{xx} \theta_H$ and the magneto-conductance $\Delta \sigma_{xx} \approx -\sigma_{xx} (\theta_H)^2$. Experiments on YBCO demonstrate that b_i is proportional to the impurity concentration and W_s is estimated to be of order of 800K [2]. Thus in the relevant temperature range the ratio of the cyclotron and charge transport relaxation times $\tau_{tr}/\tau_H \approx T/2W_s$ is small.

This is unprecedented behavior, for in conventional metals, scattering at the Fermi surface does not discriminate between transverse and longitudinal currents. Anderson [3] has proposed that two relaxation rates are evidence for two-distinct species of quasiparticle which independently relax the longitudinal and transverse currents. [4] Two alternative proposals, involving either strong momentum dependence of the electron self-energy [5–7] or singular skew-scattering [8] as the origin of two relaxation time-scales require special conditions to be realized on the Fermi surface. The former requires that the weakly scattered parts of the Fermi surface do not short-circuit the conductivity; the skew scattering model requires near-perfect particle-hole symmetry.

In this paper we reconsider the idea of two quasiparticle types. For its development, this radical idea requires an understanding of how longitudinal and transverse components of the electro-magnetic current could couple selectively to two different quasiparticles. To this end, we link the discussion with the concept of charge conjugation symmetry. [9,10] Charge-conjugation :

inter-conversion of electrons and holes, is an asymptotic low-energy symmetry of a Fermi surface. The parity $C = \pm 1$ under this symmetry operation delineates longitudinal electric currents, which are odd ($C = -1$), from transverse currents and a whole range of other neutral currents, which are even ($C = +1$). Scattering at the Fermi surface is normally “blind” to charge conjugation symmetry, leading to a single transport relaxation time. Making the tentative observation that in the cuprates, odd parity currents relax at the fast rate τ_{tr}^{-1} , whereas other even parity currents relax at the slow rate τ_H^{-1} , we are led to hypothesize that new kinds of low energy scattering processes are present in the cuprate metals which *depend on the charge conjugation symmetry of the quasiparticles*. By formulating this idea as a phenomenological transport equation we show that the fastest relaxation rate dominates the resistivity, but that the slowest relaxation rate *selectively* short-circuits all other current relaxation processes. These results constrain a large class of in-plane thermal and electric transport coefficients, allowing the hypothesis to be tested.

Consider a Fermi surface described by the Hamiltonian

$$H_o = \sum_{\vec{p}} \epsilon_{\vec{p}-e\vec{A}} \psi_{\vec{p}\sigma}^\dagger \psi_{\vec{p}\sigma}. \quad (2)$$

We define charge conjugation as

$$\psi_{\vec{p}\sigma} \longrightarrow \sigma \psi_{\vec{p}^*-\sigma}^\dagger, \quad \vec{A} \longrightarrow -\vec{A}, \quad (3)$$

where $\vec{p} = \vec{p}_F + \delta p \hat{n}$ and $\vec{p}^* = \vec{p}_F - \delta p \hat{n} + O(\delta p^2)$, locate degenerate electron and hole states along the normal $\hat{n}$ from the Fermi surface. Physical operators $\hat{O}$ can be categorized according to their *conserved* parity under charge conjugation $\hat{O} \longrightarrow C \hat{O}$, ($C = \pm 1$). For example, the electric current operator divides into independent “longitudinal” and “transverse” components $\vec{j}_e = \vec{j}_E + \vec{j}_H$,

$$\begin{aligned} \vec{j}_E &= e \sum_{\vec{p}} \vec{v}_{\vec{p}_F} \psi_{\vec{p}\sigma}^\dagger \psi_{\vec{p}\sigma} & (C = -1), \\ \vec{j}_H &= e \sum_{\vec{p}} [\underline{m}_{\vec{p}}^{-1} (\delta p - e\vec{A})] \psi_{\vec{p}\sigma}^\dagger \psi_{\vec{p}\sigma} & (C = +1), \end{aligned} \quad (4)$$

with opposite charge conjugation parities. Here, $\underline{m}_p$ is the effective mass tensor. The transverse current has the same $C = +1$ parity as the thermal current operator, and it is this term which gives rise to a Hall and thermo-electric response.

Thermal and electric transport is normally described in terms of four fundamental transport tensors [11]

$$\begin{aligned}\vec{j}_e &= \underline{\sigma} \vec{E} + \underline{\beta} \vec{\nabla} T, \\ \vec{j}_t &= \underline{\gamma} \vec{E} + \underline{\zeta} \vec{\nabla} T.\end{aligned}\quad (5)$$

These tensors are directly linked to microscopic charge and thermal current fluctuations via Kubo formulae. Table 1. compares the leading temperature dependences of the various transport tensors measured in the optimally doped cuprates with a series of calculations we now describe. The thermo-electric conductivity $\underline{\beta}$, determined from the conductivity and Seebeck coefficients, $\underline{S}$, $\underline{\beta} = -\underline{\sigma} \underline{S}$ has a particularly revealing temperature dependence. In a naïve relaxation time treatment, the temperature dependence of β is directly related to the relevant quasiparticle relaxation rate τ_{TE}^{-1} according to [12]

$$\beta = - \left(\frac{\pi^2 k_B}{3e} \right) \left(\frac{k_B T}{\epsilon_F} \right) \frac{ne^2}{m} \tau_{TE}, \quad (6)$$

where ϵ_F is the Fermi energy. Combining this with the electrical conductivity, $\sigma = \frac{ne^2}{m} \tau_{tr}$, the dimensionless thermopower is then

$$\tilde{S} = \frac{eS}{k_B} = \left(\frac{\tau_{TE}}{\tau_{tr}} \right) \left(\frac{\pi^2}{3} \right) \left(\frac{k_B T}{\epsilon_F} \right). \quad (7)$$

In optimally doped compounds [13], the thermopower contains an unusual constant part, $\tilde{S} \approx \tilde{S}_o - bT$ where $\tilde{S}_o \sim 0.1$, which indicates that

$$\tau_{TE}^{-1} = T^2 / W_{th}, \quad (8)$$

is a factor $T/\eta W_{th}$ smaller than the transport relaxation rate, where $W_{th} = (3\tilde{S}_o/\pi^2\eta)\epsilon_F \sim \epsilon_F/10$. The comparable size and temperature dependence of τ_{TE}^{-1} and τ_H^{-1} suggest that the same type of quasiparticle carries both the Hall current and the thermo-current.

By taking linear combinations of degenerate electron and hole states,

$$\begin{aligned}a_{\vec{p}\sigma} &= \frac{1}{\sqrt{2}}[\psi_{\vec{p}\sigma} + \sigma\psi_{\vec{p}^*-\sigma}], \quad (C = +1) \\ b_{\vec{p}\sigma} &= \frac{1}{i\sqrt{2}}[\psi_{\vec{p}\sigma} - \sigma\psi_{\vec{p}^*-\sigma}], \quad (C = -1)\end{aligned}\quad (9)$$

the low-energy excitations of a Fermi surface described by (1) may always be re-written as eigenstates of the charge-conjugation operator [9],

$$H_o = \sum_{|\vec{p}| > |\vec{p}_F|, \sigma} \Psi_{\vec{p}\sigma}^\dagger \epsilon_{\vec{p}-e\vec{A}\tau_y} \Psi_{\vec{p}\sigma}. \quad (10)$$

TABLE I. Leading temperature dependences of transport coefficients compared with proposed decomposition into two Majorana relaxation times ($\mathcal{L}_0$ is the Lorentz number $\pi^2 k_B^2 / 3e^2$).

Conductivity	Majorana Fluid $\times \left(\frac{m}{ne^2} \right)$	Leading T behavior		
		$\Gamma_f \gg \Gamma_s$ ($T \gg T^2$)	Expt.	Ref.
σ_{xx}	$\frac{2}{\Gamma_f + \Gamma_s}$	T^{-1}	T^{-1}	
σ_{xy}	$\frac{\omega_c}{\Gamma_f \Gamma_s}$	T^{-3}	T^{-3}	
$\Delta\sigma_{xx}$	$-\frac{\sigma_{xx}}{2} \left(\frac{\omega_c^2}{\Gamma_s^2} + \frac{\omega_c^2}{\Gamma_f^2} \right)$	T^{-5}	T^{-5}	
β_{xx}	$-\frac{eT\mathcal{L}_0}{2\epsilon_F} \left(\frac{1}{\Gamma_+} + \frac{\Gamma_+}{\Gamma_s \Gamma_f} \right)$	T^{-1}	T^{-1}	[14]
β_{xy}	$\beta_{xx} \frac{\omega_c}{\Gamma_+}$	T^{-2}	$T^{-3}(?)$	[14]
ζ_{xx}	$-\frac{\zeta_0}{2} \left(\frac{T}{\Gamma_f} + \frac{T}{\Gamma_s} \right)$	T^{-1}	(?)	[15]
ζ_{xy}	$\zeta_{xx} \frac{\omega_c}{\Gamma_+}$	T^{-2}	$T^{-1}(?)$	[15,16]

where $\Psi_{\vec{p}\sigma}^\dagger = (a_{\vec{p}\sigma}^\dagger, b_{\vec{p}\sigma}^\dagger)$, and τ_y is the second Pauli matrix. Despite the superficial resemblance with Bogoliubov quasiparticles, this is merely an alternative, if unfamiliar representation of the unpaired electron gas in terms of eigenstates of charge-conjugation, rather than eigenstates of charge. Note that from (10), photon absorption flips the charge conjugation parity of the excitation.

In this new basis the Boltzmann f function is a matrix

$$\underline{f}(\vec{p}\sigma, \vec{R}, t) = \begin{bmatrix} \langle a_{\vec{p}\sigma}^\dagger a_{\vec{p}\sigma} \rangle & \langle b_{\vec{p}\sigma}^\dagger a_{\vec{p}\sigma} \rangle \\ \langle a_{\vec{p}\sigma}^\dagger b_{\vec{p}\sigma} \rangle & \langle b_{\vec{p}\sigma}^\dagger b_{\vec{p}\sigma} \rangle \end{bmatrix}_{\vec{R}, t}, \quad (11)$$

where $\langle \rangle$ represents an appropriate coarse grained average of the microscopic Green function in the vicinity of $\vec{R}$. [17] Electric and thermal currents are given by taking the trace of $\underline{f}(\vec{p})$ with the current operators

$$j_e(\vec{p}) = e\vec{v}_{\vec{p}}\tau_y, \quad \vec{j}_t(\vec{p}) = \epsilon_{\vec{p}}\vec{v}_{\vec{p}}. \quad (12)$$

where $\vec{v}_{\vec{p}} = \vec{v}_F \underline{1} + \vec{u}_{\vec{p}} \tau_y$ is the velocity operator and $\vec{u}_{\vec{p}} = \underline{m}_{\vec{p}}^{-1} \delta \vec{p}$. The “transverse” current $\vec{j}_H = e\vec{u}_{\vec{p}}$ is diagonal in this basis whereas the “longitudinal” current $\vec{j}_E = e\vec{v}_F \tau_y$ is off-diagonal. In this representation the Boltzmann equation becomes

$$\dot{f} + \frac{1}{2} \{ \vec{v}_{\vec{p}}, \vec{\nabla}_R f \} + \frac{e}{2} \{ (\vec{E} + \vec{v}_{\vec{p}} \times \vec{B}) \tau_y, \vec{\nabla}_p f \} = I[g], \quad (13)$$

where $I[g]$ is the collision functional, $g = f - f^{(0)}$ is the departure from equilibrium. Here the curly brackets represent anticommutators, which appear when making the gradient expansion of matrix Green functions. In this phenomenological discussion we shall use the relaxation time approximation to the collision integral, which is

$$\mathcal{I}[g] = -\frac{1}{2}\{\Gamma, g\}, \quad (14)$$

where Γ is the relaxation matrix. For a conventional metal, where scattering is charge-conjugation invariant, $\underline{\Gamma} = \Gamma \underline{1}$.

So far, we have merely reformulated conventional transport theory. Our central phenomenological hypothesis is that in the cuprate metals, the relaxation times of the different Majorana modes at the Fermi surface are no longer equal. We assign “fast” (Γ_f) and “slow” (Γ_s) scattering rates to quasiparticles of opposite parity,

$$\underline{\Gamma} = \text{diag}[\Gamma_f(T), \Gamma_s(T)]. \quad (15)$$

or $\underline{\Gamma} = \Gamma_+ + \Gamma_- \tau_z$, where $\Gamma_{\pm} = \frac{1}{2}[\Gamma_f \pm \Gamma_s]$. Under this assumption, an electron is a linear combination of “fast” and “slow” eigenstates of $\hat{C}$. Since $\Gamma_f \gg \Gamma_s$, an electron will decay rapidly in time $\Delta t \sim \Gamma_f^{-1}$ into a quantum admixture of electron and hole:

$$e^- \xrightarrow{\Delta t \sim \Gamma_f^{-1}} (e^- - h^+)/\sqrt{2} \quad (16)$$

In this way, charged currents rapidly decay, leaving behind a “neutral” component which carries the slowly relaxing Hall, spin, thermal and thermo-electric currents. This is an analogue of neutral Kaon decay. [10]

Let us now follow these effects in the transport equations. Writing $g = g_o + \vec{g} \cdot \vec{\tau}$ and resolving the components of the transport equation, we obtain

$$(a + b) \begin{pmatrix} g_o \\ g_y \\ g_z \end{pmatrix} = -f' \begin{pmatrix} \Phi_{\vec{p}} \\ e\vec{E} \cdot \vec{v}_F \\ 0 \end{pmatrix}, \quad (17)$$

where $f' \equiv \partial_{\epsilon} f|_{\epsilon=\epsilon_0(\vec{p})}$, $\Phi_{\vec{p}} = e\vec{E} \cdot \vec{u}_{\vec{p}} - \epsilon_0(\vec{p})T^{-1}\vec{\nabla}T \cdot \vec{v}_F$, is the neutral current driving term and

$$a = \partial_t + \Gamma_+ \underline{1} + \Gamma_- \tau_z, \quad b = \left[e(\vec{E} + \mathcal{V}_{\vec{p}} \times \vec{B}) \underline{\mathcal{I}}_y \cdot \vec{\nabla}_{\vec{p}} + \vec{\mathcal{V}}_{\vec{p}} \cdot \vec{\nabla}T \partial_T \right], \quad (18)$$

are the collision and gradient terms, in which we have implicitly made the transformation

$$\underline{\mathcal{I}}_y \rightarrow \begin{pmatrix} 0 & 1 & 0 \\ 1 & 0 & 0 \\ 0 & 0 & 0 \end{pmatrix}, \quad \underline{\mathcal{I}}_z \rightarrow \begin{pmatrix} 0 & 0 & 1 \\ 0 & 0 & 0 \\ 1 & 0 & 0 \end{pmatrix}. \quad (19)$$

The equation for g_x decouples and has been omitted.

To solve the transport equations, we adopt the standard Zener-Jones multipole expansion, inverting (17) and expanding order by order in powers of (b/a) , $g = g^{(1)} + g^{(2)} + \dots$, where $g^{(n)} = (-a^{-1}b)^{n-1}g^{(1)}$. By expanding the leading contributions to the electrical and thermal currents

$$\begin{aligned} \vec{j}_e &= e \sum [\vec{v}_F g_y(\vec{p}) + \vec{u}_{\vec{p}} g_o(\vec{p})], \\ \vec{j}_t &= \sum \epsilon(\vec{p}) [\vec{v}_F g_o(\vec{p}) + \vec{u}_{\vec{p}} g_y(\vec{p})]. \end{aligned} \quad (20)$$

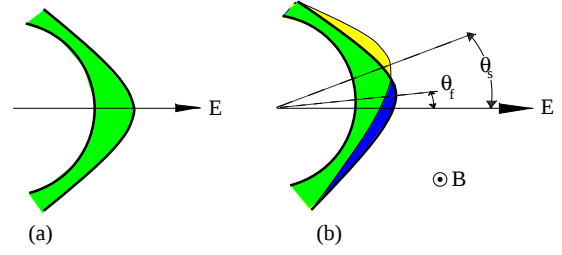


FIG. 1. (a) Application of field creates a mixture of slowly and rapidly relaxing quasiparticles. (b) Slow and fast component of the Majorana fluid precesses in a field, equilibrating at large and small Hall angles respectively.

we obtain the transport coefficients. The results for a simplified parabolic band are summarized in Table 1.

A simple physical picture of the effect of an electric field is provided in Fig. 1. When an electric field is applied, it produces an admixture of $C = +1$ and $C = -1$ quasiparticles whose joint relaxation rate $\Gamma_{tr} = \frac{1}{2}[\Gamma_s + \Gamma_f] \approx \frac{1}{2}\Gamma_f$ is dominated by the rapidly relaxing quasiparticles. Magnetic fields couple diagonally to the Majorana quasi-particles, deflecting each component through a Hall angle $\theta_{s,f} = \omega_c/\Gamma_{s,f}$. Since $\theta_s \gg \theta_f$, the Hall current is dominated by the slow-relaxation quasiparticles.

A thermal gradient couples diagonally to the quasiparticles, so thermal and thermo-electric conductivities are determined by the slow relaxation rate. The difference in the relaxation times of the electrical and thermo-electric currents then gives rise to the unique temperature independent component in the Seebeck coefficient $S = -\rho\beta \propto (T\Gamma_f/\Gamma_s)$. The off-diagonal field-dependent part of the thermal conductivity, is of interest because it is free from phonon contributions. The field-dependent part of thermal current is even under the charge conjugation operator, so the thermal Hall angle is determined by the fast relaxation rate, $\theta_T \sim \omega_c/\Gamma_+$, giving $\zeta_{xy} \sim 1/T^2$. Provisional measurements of the Hall conductivity [16] show that it grows as the temperature is lowered, but suggest $\zeta_{xy} \sim 1/T$, a result which if sustained, would refute our approach.

Various experiments can be used both to test and contrast our picture with alternative theories. Most importantly, we predict that the fast relaxation rate will only appear in charge-conjugation-odd currents; all other currents will be short-circuited by the slowly relaxing quasiparticles. A.C. Hall conductivity $\sigma_{xy}(\omega)$ is another discriminatory probe. Provided $\Gamma_s \ll \Gamma_f$, our model predicts

$$\cot \theta_H(\omega) = \frac{\sigma_{xx}(\omega)}{\sigma_{xy}(\omega)} = \left(\frac{-i\omega + \Gamma_s(T)}{\omega_c} \right). \quad (21)$$

In the skew-scattering model [8], $\omega_c \rightarrow \omega_c^*(T) \propto \frac{1}{T}$ is renormalized and there is only one relaxation rate

$\Gamma_s = \Gamma_f$, so $Im[\cot \theta(\omega)] \propto \omega T$ is proportional to temperature. By contrast, in the two-relaxation time scenario, this quantity is temperature independent. The extension of existing A.C. Hall measurements on *YBCO* [18] to a variety of temperatures can thus delineate these two scenarios.

Symmetry arguments have led us to suggest that if Hall and electric currents decay at qualitatively different rates, the imaginary part of the electron self-energy has the form

$$\Gamma = \Gamma_+ + \Gamma_- \hat{C}, \quad (22)$$

where $\hat{C}$ is the charge conjugation operator. We now discuss the interpretation of this hypothesis. Microscopically, terms proportional to $\hat{C}$ represent the inelastic inter-conversion of electrons and holes. This is superficially similar to “charge imbalance relaxation” in superconductors, where inelastic collisions give rise to a relaxation of quasiparticle charge into the condensate at a rate Γ_Q . [19,20] Evidently we have no condensate, but for consistency we do need a coherent charge reservoir to which charge is transferred by anomalous scattering events; its coherence length has to be *finite*, but it must also be long compared with the quasiparticle mean-free path

$$\xi(T) \gtrsim v_F / \Gamma_s(T). \quad (23)$$

We are thus tempted to interpret $\Gamma_- \sim 2T$ as a charge relaxation rate which survives in the normal state by virtue of these large coherent patches. It may be possible to directly test this idea, for once the cuprate metals become superconducting, the charge relaxation rate can be measured using a NSN tunnel junction [19] or phase slip centers in narrow wires. In conventional superconductors as $T \rightarrow T_c$, $\Gamma_Q \rightarrow 0$; [19,20] in the cuprates we expect the charge imbalance decay rate to remain finite as $T \rightarrow T_c$.

These lines of reasoning suggest the presence of a mutual inelastic decay channel for electrons and holes $h^+ \rightleftharpoons \text{neutral state} \rightleftharpoons e^-$ which involves the emission or absorption of a charge $+1e$ object into the charge reservoir. Perhaps there is a loose link here with the “holon” excitation in Anderson’s Luttinger liquid scenario? [3] We also note that recent theoretical work on non-Fermi liquid behavior in impurity models indicates one origin of scale-invariant marginal Fermi liquid behavior [21] is the formation of fermionic three-body bound-states with *definite* charge conjugation symmetry. [22,23] The formation of such objects around the Fermi surface, might provide a microscopic basis for our phenomenological hypothesis.

In summary, we have proposed that the appearance of two transport relaxation times in the cuprate metals is a consequence of scattering effects that are sensitive to the charge conjugation symmetry of the quasiparticles. We have formulated this hypothesis in a transport equation

where one eigenstate of charge-conjugation symmetry decays much more rapidly than its partner. The decay of electric current is dominated by the rapid relaxation rate while “neutral” transport currents, including the Hall and thermo-electric currents, are governed by the slower decay rate.

We should like to thank E. Abrahams, P. W. Anderson, G. L.onzarich and Ph. Ong for discussions related to this work. We are indebted to O. Entin-Wohlman for identifying a possible link with charge transfer imbalance in superconductors. This research was supported by travel funds from NATO grant CRG 940040 (AMT & PC), NSF grants DMR-93-12138 (PC) and a travel fellowship from the Royal Society (AJS).

-
- [1] E.g. M. Gurvitch and A. T. Fiory, Phys. Rev. Lett. **59**, 1337 (1987); L. Forro *et al.*, *ibid.* **65**, 1941 (1990).
 - [2] T. R. Chien, Z. Z. Wang and N. P. Ong, Phys. Rev. Lett. **67**, 2088 (1991); J. M. Harris *et al.*, Phys. Rev. Lett. **75**, 1391 (1995).
 - [3] P. W. Anderson, Phys. Rev. Lett. **67**, 2092 (1991)
 - [4] D. B. Romero, Phys. Rev. **B 46**, 8505 (1992).
 - [5] A. Carrington, A. P. Mackenzie, C. T. Lin and J. R. Cooper, Phys. Rev. Lett. **69**, 2855 (1992).
 - [6] R. Hlubina and T. M. Rice, Phys. Rev. B **51** 9253, (1995).
 - [7] B. P. Stojkovic and D. Pines, cond-mat/9505005 (1995).
 - [8] B. G. Kotliar, A. Sengupta and C. M. Varma, preprint (1995).
 - [9] E. Majorana, Il Nuovo Cimento, **14**, 171 (1937).
 - [10] M. Gell-Mann and A. Pais, Phys. Rev. **97**, 1387 (1955).
 - [11] $\underline{\beta}$ and $\underline{\gamma}$ are linked by the Onsager relation $\underline{\gamma}(B) = -T \underline{\beta}^T(-B)$, where B is the magnetic field.
 - [12] E.g. A. A. Abrikosov, *Fundamentals of the Theory of Metals*, Elsevier Science Pub. Co., New York, p. 103 (1988).
 - [13] S. D. Obertelli, J. R. Cooper and J. L. Tallon, Phys. Rev. B, **46**, 14928 (1992).
 - [14] $\underline{\beta} = \underline{\sigma} \underline{S} \approx \underline{\sigma} \underline{S}_{xx}$, since the Nernst Ettinghausen coefficient is negligible ($|S_{xy}|/S_{xx} \ll \sigma_{xy}/\sigma_{xx}$): see J. A. Clayhold, A. W. Linnen Jr., F. Chien and C. W. Chu, Phys. Rev. B **50**, 4252, (1994).
 - [15] $\underline{\zeta} = -\underline{\kappa} + T \underline{\beta}^T(-B) \underline{\sigma} \underline{\beta}(B)$ with the leading temperature dependence coming from the thermal conductivity $\underline{\kappa}$. The κ_{xx} is phonon dominated: see C. Uher, in *Physical properties of high temperature superconductors: vol III* p. 159, editor D. M. Ginsberg, World Scientific, Singapore (1992).
 - [16] K. Krishana, J. M. Harris and N. P. Ong, preprint (1995).
 - [17] L. P. Kadanoff and G. Baym, *Quantum statistical mechanics*, W. A. Benjamin, New York (1962).
 - [18] S. G. Kaplan *et al.*, preprint (1995).
 - [19] J. Clarke, Phys. Rev. Lett. **28**, 1363, (1972).
 - [20] See C. J. Pethick and H. Smith, p 481 in “*Non Equilibrium Superconductivity, Phonons and Kapitza bound-*

- aries*, ed. K. E. Gray, Plenum, NY (1981).
- [21] C. M. Varma, P. B. Littlewood, S. Schmitt-Rink, E. Abrahams and A. E. Ruckenstein, Phys. Rev. Lett. **63**, 1996, (1989).
 - [22] A. E. Ruckenstein and C. M. Varma, Physica **C 185-189**, 134, (1991).
 - [23] P. Coleman, L. Ioffe and A. M. Tsvelik, Phys. Rev. **B52**, 6611 (1995).